

METRIC

Brass Alloy SM 1065

Comparable standards

ISO:	CuZn35
ASTM:	UNS 27000
EN:	CW 507L
JIS:	C2700

Chemical Composition

Element	Unit	Range
Copper	%	64.5 - 66.5
Lead	%	max. 0.05
Iron	%	max. 0.05
Zinc	-	remainder

Dimensions

Nominal width mm	Tolerance
- 50	± 0.05
50 - 100	± 0.075
100 - 200	± 0.10
200 - 400	± 0.15
400 - 600	± 0.20

Nominal thickness mm	In steps of
0.080 - 0.250	0,005
0.250 - 0.400	0,010
0.400 - 1.000	0,050
1.000 - 2.000	0,100

Notes:

- Unslitted width [full master coil width] possible [app. 640 mm wide]
- Thickness tolerance up to 0.150 mm nominal: ± 0.003 mm
- Thickness tolerance over 0.150 mm nominal: ± 2% [rounded upwards to nearest micron]

Physical Properties

Density	kg/m ³	8450
Melting temperature	°C	902-940
Specific heat	kJ/(kg °C)	0.38
Electrical conductivity	MS/m	15
Electrical conductivity	IACS %	26
Electrical resistivity	nΩ meter	67
Thermal conductivity	W/(m °C)	121
Thermal expansion 20-300°C	10 ⁻⁶ °C ⁻¹	20.2
Young's modulus E	MPa	110 000

Brass Alloy SM 1065

Mechanical Properties - Standardized Tempers

Temper			Yield R _{p0,2} MPa	Tensile R _m MPa	Elongation A ₅₀ %	Hardness HV	Grain size µm
Luvata	ASTM	Comments					
Annealed to temper							
72				300-370	20-	65 - 85	
77	O82	½ Hard	(260-)	380-460	21-	96-124	<10
79		HF welding		440-480		115-145	<10
Rolled to temper							
86B	H 02	½ Hard		390-480	20-	118-148	<15

Mechanical Properties - Non Standardized Tempers


Temper			Yield R _{p0,2} MPa	Tensile R _m MPa	Elongation A ₅₀ %	Hardness HV	Grain size µm
Luvata	ASTM	Comments					
Annealed to temper							
71		Soft	(-160)	280-360	40-	60-80	
74				330-390		75-95	
75	O81	1/4 Hard	(170-)	350-410	21-	80-100	
76				370-430		88-112	
78				420-470	9-	105-135	
79				440-480		115-145	
Rolled to temper							
82	H 01	1/4 Hard		340-405		95-115	
83				355-420		103-127	
84				370-435		108-135	
85				380-450		113-143	
87				410-480		125-155	
88				425-495		132-162	
89	H 03	3/4 Hard		440-510		140-170	
91				465-535		145-175	
92	H 04	Hard		490-560		160-190	
93				515-585		170-200	
95	H 06	Extra Hard		565-635		180-210	
97	H 08	Spring		615-685			

Notes:

- Material is produced to stated hardness requirements
- Stated ranges for yield strength, tensile strength, elongation and grain size are typical values, and for information only

Brass Alloy SM 1065

Heat Resistance and Softening Characteristics

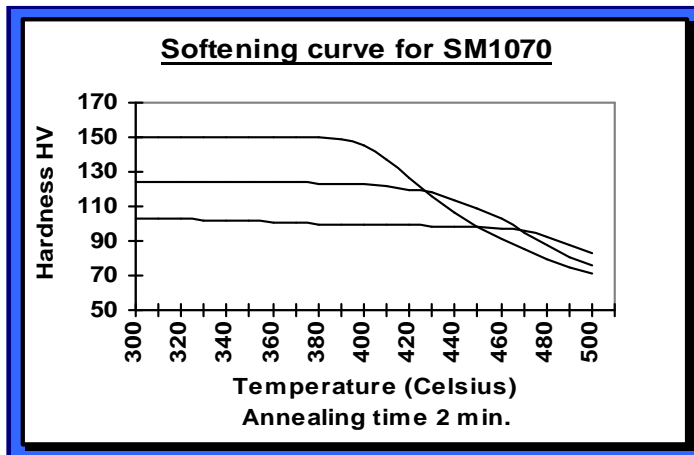

Softening characteristics.

(Temperatures at 1 min annealing time will be 10 degrees higher)

(Temperatures at 4 min annealing time will be 10 degrees lower)

Heat Treatment

Soft annealing

450 - 550 °C

Time dep. on size and volume: propose

2 hours

Stress relief annealing

275 - 325 °C

Welding

Due to the very high zinc content, some counter-measures to stop vaporization of zinc are necessary. Otherwise the alloy is suitable for soldering, brazing and welding.

Brass Alloy SM 1065

Formability

Valid for all tempers:
Both at elevated as well as room temperature
easy to form, however decreasing with increased hardness.

Below: minimum bending radius. t = gauge

Temper	Hardness	t = < 0.25 mm		t = > 0.25 mm	
		good way	bad way	good way	bad way
Soft	HV 65-125	0 x t	0 x t	0 x t	0 x t
Hard	HV 120-155	0 x t	0 x t	0 x t	1 x t
	HV 150-180	0 x t	1 x t	0 x t	2 x t
	HV 170-200	0 x t	2 x t	1 x t	3 x t

Surface Treatment.


Colours are gold- to yellowish but could easily be influenced by many types of surface treatments.

Brass Alloy SM 1065

Corrosion Properties

Durable to water and organic compounds, as well as land-, sea- and industrial atmospheres.

Dezincification comparison:

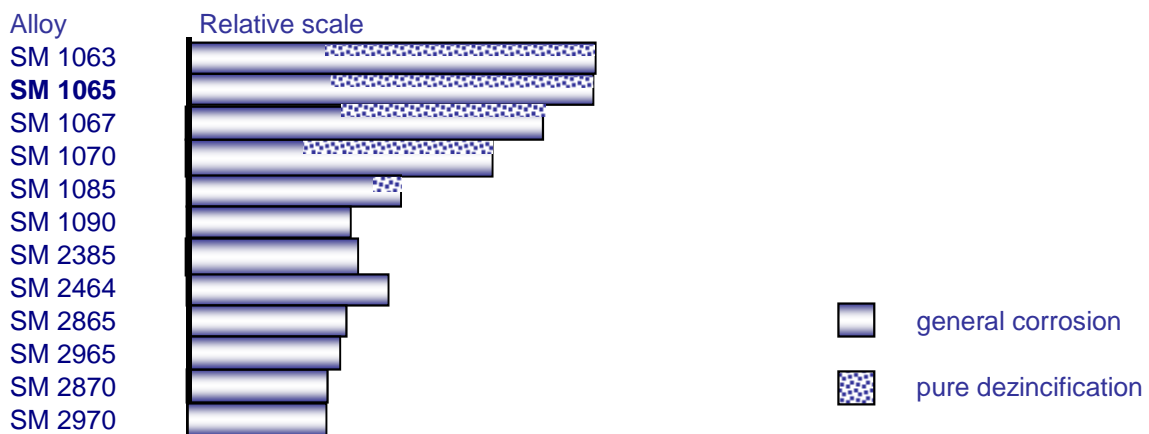

SM 1065 is the base alloy widely used and suitable for many radiator applications.

To minimize the risk for **stress corrosion cracking** we strongly recommend stress-relief annealing after all cold forming operations.

In general the higher the copper content, the better the resistance to stress corrosion cracking.